


4563 Three Bushing Compression Graph

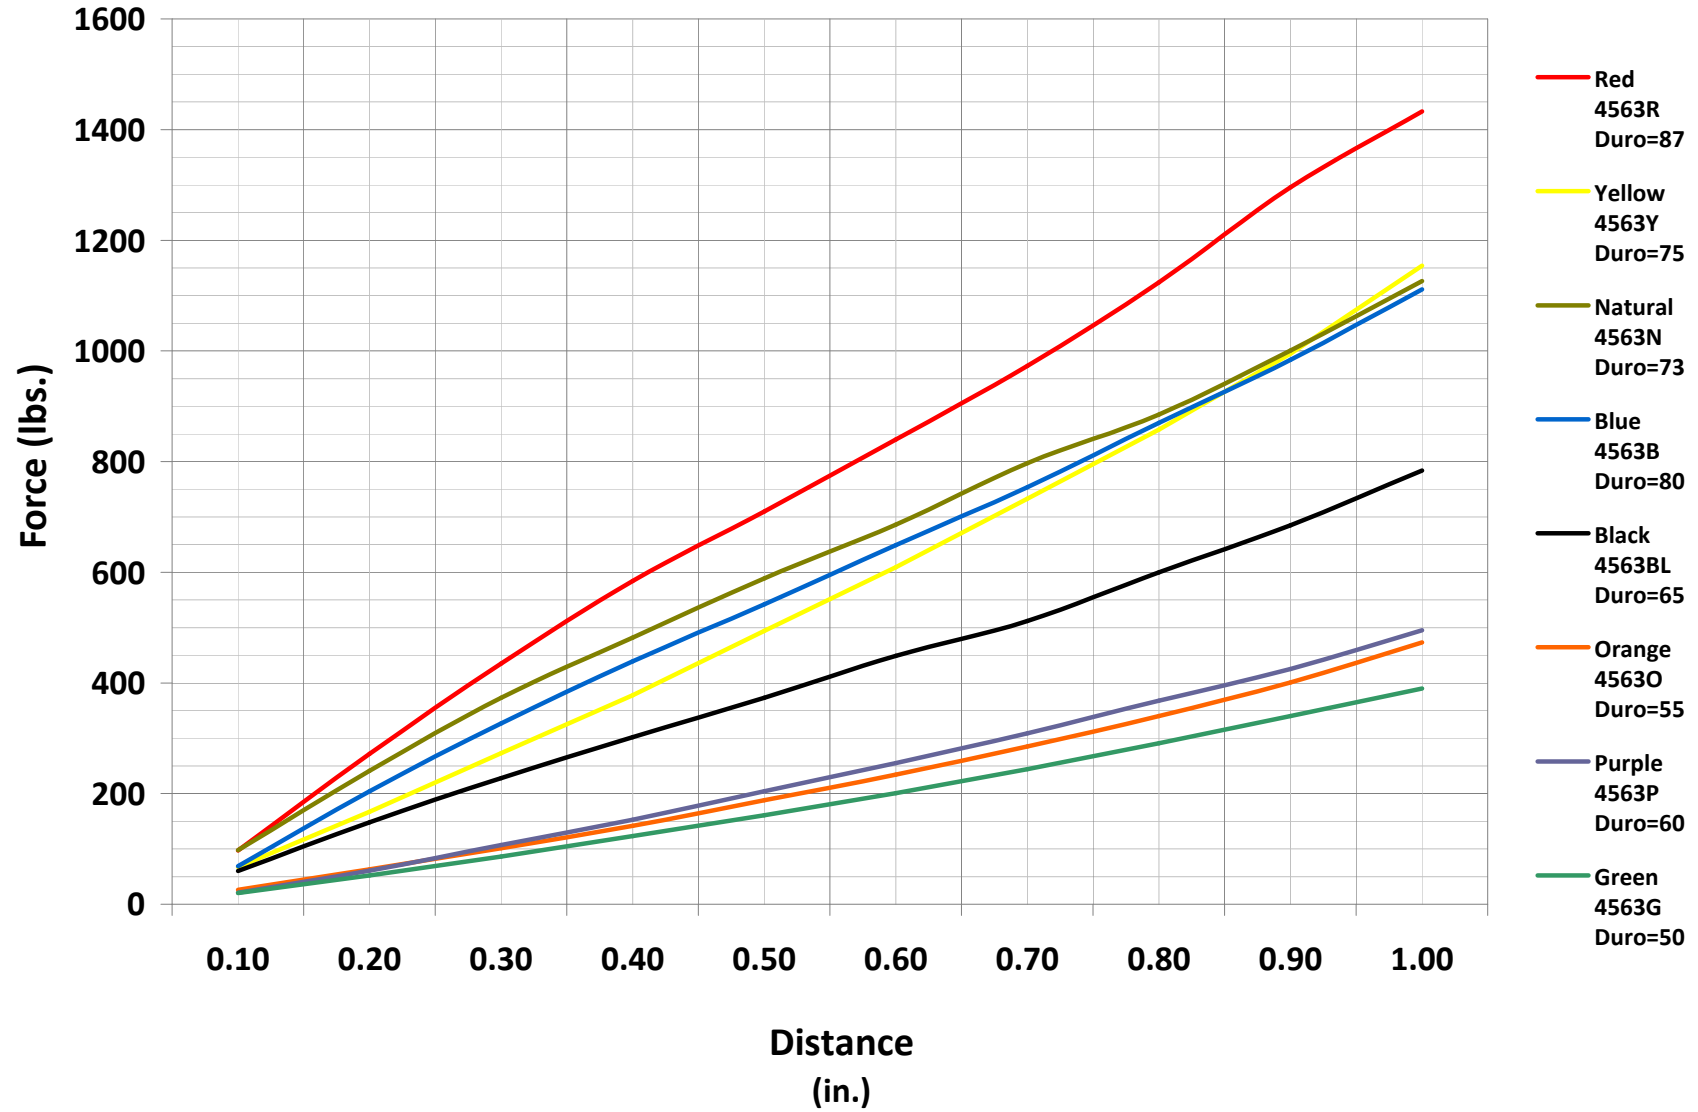

4563 Three Bushing Compression Test

	0.10	0.20	0.30	0.40	0.50	0.60	0.70	0.80
Red 4563R Duro=87	97	272	435	584	710	840	973	1124
Yellow 4563Y Duro=75	67	167	273	378	494	609	733	858
Natural 4563N Duro=73	98	241	373	482	589	686	797	885
Blue 4563B Duro=80	69	204	327	439	542	649	754	870
Black 4563BL Duro=65	60	148	228	302	373	449	512	600
Orange 4563O Duro=55	26	63	101	142	188	234	285	340
Purple 4563P Duro=60	21	61	107	153	204	255	309	368
Green 4563G Duro=50	20	52	86	123	161	201	244	291

0.90	1.00
1296	1433
995	1154
1001	1126
984	1111
685	784
401	473
425	495
340	390